



Solvent Extraction of Zinc from Burnt Tyre Ash using Tri Butyl Phosphate

Oke Temidayo Joseph ^{a*}, Ayowole Awwal ^b,
Kehinde Israel Omoniyi ^c, Nkwocha Stephen Tochi ^d,
Kayode Medubi ^e and Adebayo Abisola Alice ^f

^a Department of Chemistry and Biochemistry, University of Wisconsin-Milwaukee, United States.

^b Department of Chemistry, University of Western Illinois, United States.

^c Department of Chemistry, Ahmadu Bello University, Nigeria.

^d Department of Chemistry and Biochemistry, University of Wisconsin Milwaukee, United States.

^e Department of Chemistry, University of Wisconsin Milwaukee, United States.

^f Department of Microbiology, Kwara State University, Nigeria.

Authors' contributions

This work was carried out in collaboration among all authors. All authors read and approved the final manuscript.

Article Information

DOI: <https://doi.org/10.9734/CSJI/2024/v33i5912>

Open Peer Review History:

This journal follows the Advanced Open Peer Review policy. Identity of the Reviewers, Editor(s) and additional Reviewers, peer review comments, different versions of the manuscript, comments of the editors, etc are available here:

<https://www.sdiarticle5.com/review-history/121724>

Original Research Article

Received: 12/06/2024

Accepted: 14/08/2024

Published: 21/08/2024

ABSTRACT

The article reports the solvent extraction of zinc (Zn) from burnt tyre ash using tributylphosphate (TBP) as an extractant. The increasing interest in environmental protection and resource recovery has prompted research into extracting valuable metals from waste materials, such as Zn from tyre ash, a significant secondary source. The optimal conditions for Zn leaching and extraction were determined through a series of hydrometallurgical processes. Zn was successfully extracted under specific HCl concentration, temperature, and pH conditions, with TBP showing effective performance as an extractant. We found that increasing the initial concentration of TBP in

*Corresponding author: E-mail: temidayooke2016@gmail.com;

kerosene improves the extraction efficiency of Zn from burnt tyre ash. The highest extraction rate achieved was 48.68% using 0.30 mol/L TBP at pH 4.5. The relationship between log D and log [TBP] was done to determine how many moles of TBP were involved in the extraction system. A linear plot with a slope of ~ 1.00 was obtained and indicated the liberation of one mole of [H⁺] while extracting one mole of Zn²⁺ from the burnt tyre ash. The study highlights the potential for resource recovery from waste materials, contributing to both environmental sustainability and the supply of industrial metals.

Keywords: Zn; Burnt tyre ash; leaching; Tributylphosphate (TBP); extraction; environmental protection; industrial waste.

1. INTRODUCTION

With the growing interest in environmental protection in recent years, among the concerns under discussion are emissions of hazardous chemical species during waste incineration, spontaneous combustion of the waste in storage, and secondary pollution by heavy metals highly concentrated in the combustion residue.

Automobile tyres contain rubber, carbon black, and various organic and inorganic additives (including plasticizers, anti-aging agents, sulfur and ZnO, etc) [1,2]. Heavy metals are concentrated in combustion ashes during incineration, and the residues are disposed of as industrial waste under strict regulation. However, whole tyre wastes annually generated an estimated value of 7000 tonnes for Zn, drawing attention to the recovery of valuable metals from waste scrap and dumpsite ashes [3].

Zn is one of the minerals that has been neglected previously but is recently gaining importance as a base metal for various applications in the metallurgical and chemical industry [4] it is widely extracted from its primary ore (sphalerite) and can also be recovered from secondary sources [5,6], such as Zn ash, Zn dross, flu dust of electric arc and automobile shredder scrap. The chemical nature of the secondary source is such that they are classified as hazardous waste, and their toxicity is mainly due to the presence of different metals such as lead, cadmium, cobalt, arsenic, and chromium [7]. Therefore, with the depletion of the primary sources of metal, researchers have begun to search for alternatives, which has resulted in metals like Zn now being extracted from secondary sources like galvanizing plant dross and ash, spent primary batteries, Zn scrap, leach residue flue dust generated from iron making and steel making plant however spent galvanizing [7].

Much work has been reported in the literature regarding the use of extractants of diverse nature

and in various media, such as dithizone and cyclohexanones, which have limited solubility in organic solvents and so are not recommended when Zn concentration is greater than 10–3 mol/L. Carboxylic acids, amines, organophosphorus compounds, and chelex-100 have been cited as good candidates for the extraction of Zn [7].

TBP (Tributylphosphate) has been cited to be a good candidate for the extraction of Zn (II) in acid media [8]. There is practically little or no information on the ability of triphenylphosphine (TPP) to extract Pb or Zn, except a report on its use for the extraction of palladium [9].

Zn ash is an important secondary source of Zn recovery as it constitutes a source from which a high amount of Zn can be recovered. Pyrometallurgical and hydrometallurgical processes are employed in the treatment of secondary sources, and they are more environmentally friendly and cost-effective in treating Zn-containing materials through leaching and selective precipitation by solvent extraction [10].

The hydrometallurgical process usually involves the dissolution of the secondary sources (sometimes after ashing) in an acidic media, sometimes with prior water treatment, and recovering the Zn from the solution. Ammonium carbonate has been used for Zn recovery from steel dust, automobile scrap, and incinerator fly ash [11] in the latter case, with a 400 C roasting step included. Combination treatments have also been used, such as sulphuric acid and chloride leaching with electro-galvanizing dust, waste acid and alkali for fly ash, sulphuric acid and sodium bisulphide/carbonate for flue dust, and a combination of acid/oxygen/ H₂O & S₂O, with blast furnace dust. Sulphuric acid leaching has been used for steel dust, and it is the most commonly used approach for the solubilization of solid Zn waste solids [12]. About 30-40% of Zn

consumed comes from reclaimed Zn sources [13,11]. Pyrometallurgical processes generally involve heating at temperature (usually in the furnace), the secondary sources of Zn to remove the non-metallic content of the sample, and then leaching the Zn-rich ash in suitable acid. It is employed in the processing of most metals and finds application in the extraction of base metals like Zn, tin, etc. Researchers have used extractants such as TBP to exploit the recovery of Zn from spent batteries [14].

1.1 Extractant

Tributylphosphate is an organophosphorus compound with the chemical formula $(\text{CH}_3\text{CH}_2\text{CH}_2\text{CH}_2\text{O})_3\text{PO}$. It is a colorless and odorless liquid, and its application is found in its use as an extractant and a plasticizer [15]. It is an ester of phosphonic acid with n-butanol. It is used as a solvent for extracting and purifying rare earth metal from the ores. An extractant aims to provide high selectivity and efficiency for metal chelation. It is also referred to as a solvating extractant.

1.2 Leaching

Leaching involves the removal of contaminants (organic or inorganic) from a solid state into a liquid phase when a substance is subjected to different processes, such as mineral dissolution, complexation, and desorption [16]. Leaching is one of the important processes involved in the field of metallurgy [5].

2. SIGNIFICANCE OF THE STUDY

Zn is an important industrial metal used in various applications, including galvanizing steel, manufacturing brass, and other alloys, and producing batteries, paints, and fertilizers widely used in industries such as construction, automotive, electrical, and electronics [17-19].

Zn has also been used as an anode in many historical galvanic elements. These include, among others, the Voltasche column, the Daniell element, and the Bunsen element. To a lesser extent, Zn is also used for negative electrodes in accumulators (rechargeable batteries); Zn is mixed with small amounts of other metals. These include lead, bismuth, indium, aluminum, and calcium. Zn die casting is the common name for die-cast parts made of refined Zn casting alloys. These alloys provide far better casting values than are possible when casting pure Zn. Zn was

used in times of need, most recently in the two world wars, in the form of Zn alloys for coinage. The global Zn market is influenced by supply and demand dynamics, global economic conditions, technological advancements, and factors [20] hence the drive for the demand for Zn is ores and products.

3. METHODS

3.1 Sample Collection

Burnt tyre ashes (1 kg) were collected from a waste dumpsite in the Dogarawa area of Zaria, Kaduna state, Nigeria, in November 2022. Tyres were burned after a regulatory agency confiscated them.

3.2 Protocol

Ash (2.5 g) was dissolved in aqua regia (250 ml) at an ambient temperature of 25 °C for less than 2 hours (1:3 of HCl: HNO₃), and the total concentration of Zn in the ash was measured in the resulting solution by atomic absorption Spectrophotometry after filtration and dilution.

3.3 Determination of Total Zinc Content in the Dumpsite Ash and Optimum Leaching Condition for Zn

The optimum leaching conditions of HCl concentration, temperature, leaching time, and agitation speed were determined and are 2.968 mol/L of HCl, 68.85, 97 minutes, at an agitation rate of 400 rpm. The amount of Zn leached was 32009.205 mg/L.

3.4 Leaching of Zn from the Dumpsite Ash

2.5 g of burnt tyre ash was weighed and introduced into a 250 cm³ prepared solution of HCl in a 500 cm³ beaker and was introduced on a heating magnetic stirrer at 68.85 °C. A magnetic stirrer bar was inserted, and the solution was covered with a glass lid. The burnt tyre was left to be in contact with the lixiviant for 97 minutes, at the end of the contact time, the mixture obtained was then filtered and the insoluble residue left on a filter paper was washed thoroughly with a little of the hot filtrate. The filtrate was then carefully transferred into a 250 ml standard volumetric flask. The solution was made to mark with distilled water; the filtrate in the standard volumetric flask was



Plate 1. Preparation of leach liquor

then adjusted to pH 3.5 with a pH meter before analysis, using Atomic Absorption Spectroscopy (AAS) as presented in Plate 1.

3.5 Preparation of TBP Solution

Tributylphosphate ($(\text{CH}_3\text{CH}_2\text{CH}_2\text{CH}_2\text{O})_3\text{PO}$) has an assay % Purity = 99%, Specific gravity = 0.98 g/cm^3 , Molar mass = 266 g/mol

Calculation of molarity of the stock TBP

$$M = \frac{\%P \times Spg \times 10}{Mm}$$

$$M = \frac{99 \times 0.98 \times 10}{266}$$

$$M = 3.65 \text{ M (concentration of the stock TBP)}$$

Using the dilution formula, the volume of TBP needed to prepare a standard solution can be calculated.

$$C_1V_1 = C_2V_2$$

To prepare 0.30M TBP

$$V_1 = \frac{0.30 \times 50}{3.65}$$

$$V_1 = 4.10 \text{ cm}^3$$

About 4.10 cm^3 of TBP was measured and slowly added to 25 cm^3 kerosene in a 50 cm^3 volumetric flask and made up to the 50 cm^3 volume with kerosene.

The same process was carried out for the preparation of other concentrations of TBP which were 0.05 M, 0.10 M, 0.15 M, 0.20 M, 0.25 M, and 0.30 M.

3.6 Procedure for the Solvent Extraction of Zn from Leach Liquor

The experiment was performed using the leachate obtained by the optimal conditions of

the temperature leaching, concentration, and time of Zn in the leached liquor in section 3.4. AAS carried out analysis at room temperature 25 ± 2 $^\circ\text{C}$. Equal volumes of 10 cm^3 of the predetermined concentration of the extractant (TBP), which were 0.05 M to 0.30 M TBP with 10 cm^3 of leachate from section 3.4 were mixed in a 250 cm^3 conical flask and shaken using a mechanical shaker for 25 minutes at room temperature. The pH of the pregnant leach solution in each case was ensured to be pH 4.5. Plate 2 presents the preparation of the aqueous and organic phases.

After the equilibration phase disengagement was carried out for each experimental group in a 250 cm^3 separating funnel, it was allowed to form two separation layers. The upper one contained Zn loaded organic phase while the lower part had a clear solution, after the formation of two distinct layers the clear solution (aqueous phase) was drained out by opening the tap. The concentration of Zn in each experimental group of TBP concentration was calculated using AAS analysis, to determine the Zn composition left in the aqueous phase.

The concentration of the metal in an organic phase was calculated from the differences between its concentration in the aqueous phase before and after the extraction [21]. Then % of Zn extracted against TBP concentration was plotted.

3.7 Effect of pH on the Solvent Extraction of Zn

The percentage of extracted Zn against the concentration of TBP that gave the highest percentage of co-extracted was used for the optimization of other parameters which included the equilibrium pH of the aqueous media [22]. The pH of the leach liquor in section 3.4 was adjusted to a pH of 2.5, 4.5, and 5.5, and the % of Zn extracted using solvent extraction was repeated for each case as in section 3.6. The optimum pH was then determined. A plot of % Zn extracted against pH was plotted.



Plate 2. Preparation of aqueous phase and organic phase



Plate 3. Separating funnel setup

$$\% E = \frac{[M]_{org}}{[M]_{aqu.initial}}$$

$$D = \frac{[M]_{org}}{[M]_{aqu}}$$

3.8 Stripping of Zn

Zn was stripped from the loaded organic phase by contacting the experimental organic phase with a 0.05 mol/L HCl solution and shaking for 25 min thereafter; the mixture was allowed to reach equilibrium and then separated with a separating funnel. The aqueous phase contains the metals (Zn), and the organic phase will be TBP. The Zn ion concentration in the stripping aqueous was spectrophotometrically measured using AAS.

4. RESULTS AND DISCUSSION

Calculation:

Formula for leaching

$$\text{Actual concentration} = \text{Instrument reading} \times \text{Dilution factor}$$

For aqueous initial

Instrument reading = 2.5477 ppm,

Dilution factor = 100

Actual concentration – 254.77 mg/L or
254.77 ppm

The initial concentration of Zn in the leached gotten was 254.77 mg/L

4.1 Effect of TBP Concentration on the Extraction of Zn from Burnt Tyre Ash

The initial concentration of Zn in the leached liquor was 254.77 mg/L. The effect of the extractant concentration on the extraction of Zn from the leached liquor was carried out over the TBP concentration range of 0.05-0.30 mol/L at a pH of 4.5. The results obtained in Table 1 showed that the percentage of Zn extracted increased from 30.69% to 48.68% with an increase in TBP concentration. Thus, a plot of the percentage of Zn extraction against the TBP concentration was obtained to get the optimal TBP concentration. The highest percentage of Zn extracted was 48.68% using 0.30 M TBP at pH 4.5.

Table 1. Effect of TBP concentration on the amount of Zn unextracted from the leached liquor

[TBP]/pH	[Zn] (ppm)	SD	Mean Abs
[0.05 M] at pH 2.5	2.2353	0.0033	0.3635
[0.10 M] at pH 2.5	1.7878	0.0036	0.2907
[0.15 M] at pH 2.5	1.7074	0.0053	0.2777
[0.20 M] at pH 2.5	1.6981	0.0019	0.2761
[0.25 M] at pH 2.5	1.6511	0.0028	0.2685
[0.30 M] at pH 2.5	1.6107	0.0027	0.2619
[0.05 M] at pH 3.5	2.5260	0.0105	0.4108
[0.10 M] at pH 3.5	2.4873	0.0024	0.4045
[0.15 M] at pH 3.5	2.4571	0.0045	0.3996
[0.20 M] at pH 3.5	2.4092	0.0063	0.3918
[0.25 M] at pH 3.5	2.3516	0.0060	0.3824
[0.30 M] at pH 3.5	2.2809	0.0085	0.3709
[0.05 M] at pH 4.5	1.7656	0.0061	0.2871
[0.10 M] at pH 4.5	1.6340	0.0059	0.2657
[0.15 M] at pH 4.5	1.6292	0.0043	0.2650
[0.20 M] at pH 4.5	1.5012	0.0036	0.2441
[0.25 M] at pH 4.5	1.4420	0.0055	0.2345
[0.30 M] at pH 4.5	1.3042	0.0055	0.2121
[0.05 M] at pH 5.5	1.9604	0.0092	0.3188
[0.10 M] at pH 5.5	1.8855	0.0109	0.3066
[0.15 M] at pH 5.5	1.5793	0.0014	0.2568
[0.20 M] at pH 5.5	1.4508	0.0012	0.2359
[0.25 M] at pH 5.5	1.4348	0.0002	0.2333
[0.30 M] at pH 5.5	1.4247	0.0027	0.2317

Table 2. Effect of concentration of TBP against % Zn extracted into organic phase at pH 2.5

TBP Concentration	Instrument reading (ppm)	Actual Conc.(mg/L)	[M] org	%Extraction	Distribution ratio (D)
0.05 M	2.2353	223.53	31.24	12.26%	0.139
0.10 M	1.7876	178.76	76.01	29.83%	0.423
0.15 M	1.7074	170.74	84.03	32.98%	0.492
0.20 M	1.6981	169.81	84.96	33.35%	0.500
0.25 M	1.6511	165.11	89.66	35.19%	0.543
0.30 M	1.6107	161.07	93.70	36.79%	0.582

Table 3. Effect of concentration of TBP against % Zn Extracted into organic phase at pH 3.5

TBP concentration	Instrument reading (ppm)	Actual conc. (mg/L)	[M] org	% Extraction	Distribution ratio
0.05 M	2.526	252.6	2.17	0.88%	0.089
0.10 M	2.4873	248.73	6.04	2.37%	0.024
0.15 M	2.4571	245.71	9.06	3.55%	0.037
0.20 M	2.4092	240.92	13.85	5.20%	0.057
0.25 M	2.3516	235.16	19.61	7.69%	0.083
0.30 M	2.2809	228.09	26.68	10.47%	0.117

4.2 Effect of TBP Concentration on Distribution Ratio

The effect of TBP concentration on the distribution ratio D of Zn was also studied, and the result in Table 7 showed an increase from 0.206 to 0.604. The distribution ratio increased

with an increasing extractant concentration. The slope of the plot of log D against log TBP in Table 7 gave ~1.00 and indicated that 1 mole of the extractant was involved in the extraction process. One mole of [H⁺] from the extractant, TBP, was exchanged for one mole of Zn²⁺ at each process of the extraction of Zn from the

burnt tyre ash obtained from Dogarawa, Zaria, Nigeria.

4.3 Effect of pH on the Extraction Process

- The effect of pH on the extraction efficiency of Zn using TBP was systematically examined across an equilibrium pH range from 2.5 to 5.5, as detailed in Table 6. The extraction efficiency, expressed as the percentage of Zn extracted was plotted against pH. The data indicated a positive correlation between the pH of the aqueous phase and the extent of zinc extraction, with

extraction efficiency increasing progressively as the pH increases. Notably, at pH 4.5, the extraction efficiency reached its peak, with approximately 48.68% of ZnO being successfully extracted from the burnt tire ash. This observation suggests that pH 4.5 represents the optimal condition for zinc extraction using TBP, under which the maximum yield was achieved.

4.4 Effect of TBP Concentration

The plot of log D against log [TBP], as shown in Fig. 2, demonstrates that the distribution ratio

Table 4. Percentage of Zn extracted into the organic phase with TBP concentration at pH 4.5

Concentration TBP	Instrument reading (ppm)	Actual conc. (mg/L)	[M]org	% Extraction	Distribution ratio (D)
0.05 M	1.7656	176.56	78.21	30.69%	0.443
0.10 M	1.634	163.4	91.37	35.86%	0.559
0.15 M	1.6292	162.92	91.85	36.05%	0.564
0.20 M	1.5012	150.12	104.65	41.08%	0.697
0.25 M	1.4421	144.21	110.57	43.39%	0.767
0.30 M	1.3042	130.42	124.03	48.68%	0.947

Table 5. Effect of concentration of TBP against % Zn extracted into organic phase at pH 5.5

TBP concentration	Instrumental reading(ppm)	Actual concentration	[M]org	%Extraction	Distribution ratio
0.05 M	1.9604	196.04	58.72	23.05%	0.299
0.10 M	1.8855	188.55	66.22	25.99%	0.351
0.15 M	1.5793	157.93	96.84	38.01%	0.613
0.20 M	1.4508	145.08	109.65	43.04%	0.756
0.25 M	1.4348	143.48	111.29	43.68%	0.776
0.30 M	1.4247	142.47	112.3	44.08%	0.762

Table 6. Summary of the effect of concentration of TBP against pH of the extraction of Zn

Concentration of TBP	pH 2.5	pH 3.5	pH 4.5	pH 5.5
0.05 M	0.139	0.024	0.443	0.299
0.10 M	0.423	0.037	0.559	0.351
0.15 M	0.492	0.057	0.564	0.613
0.20 M	0.500	0.087	0.694	0.756
0.25 M	0.543	0.089	0.767	0.762
0.30 M	0.582	0.117	0.942	0.776

Table 7. Effect of concentration of TBP against distribution ratio

Concentration of TBP	log x	Distribution ratio	log D
0.05 M	-1.30103	0.206	-0.68613
0.10 M	-1	0.343	-0.46471
0.15 M	-0.82391	0.436	-0.36051
0.20 M	-0.69897	0.508	-0.29414
0.25 M	-0.60206	0.539	-0.26841
0.30 M	-0.52288	0.604	-0.21896

Where $x = [TBP]$

(D) increases with increasing [TBP] concentration. The linearity of the plot, with a slope of approximately 1, indicates that one mole of $[H^+]$ is liberated during the extraction of one

mole of Zn^{2+} from the burnt tire ash. This linear relationship observed in Fig. 2 suggests a straightforward stoichiometric interaction between TBP and Zn^{2+} during extraction.

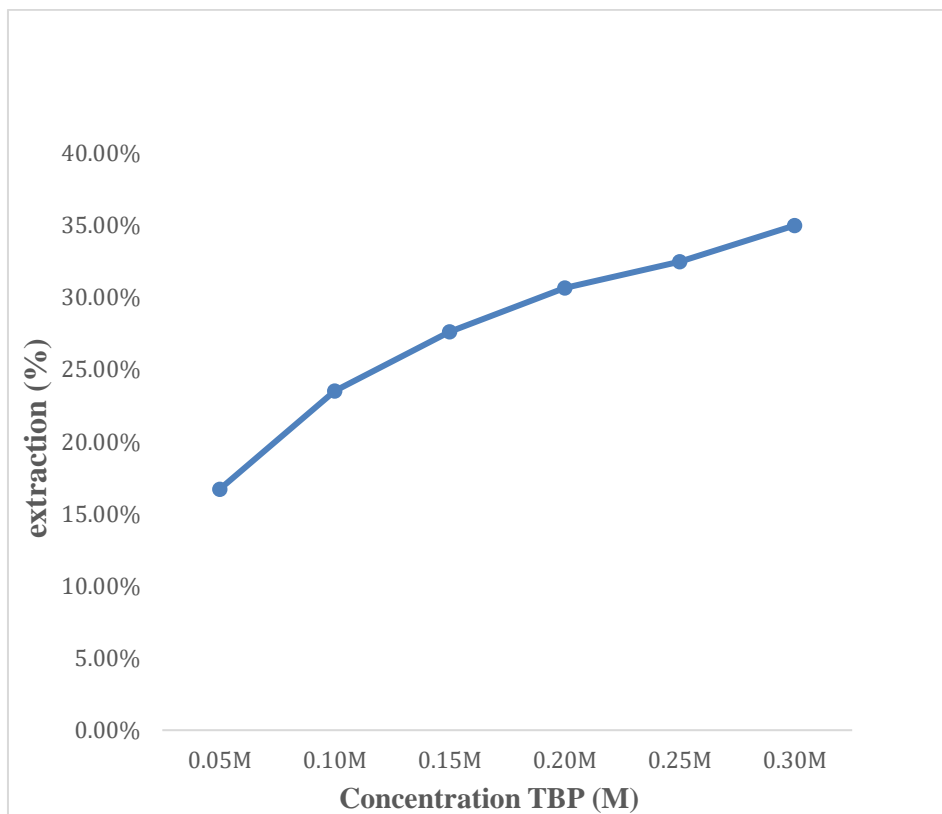


Fig. 1. Plot of % of Zn extracted against concentration of TBP

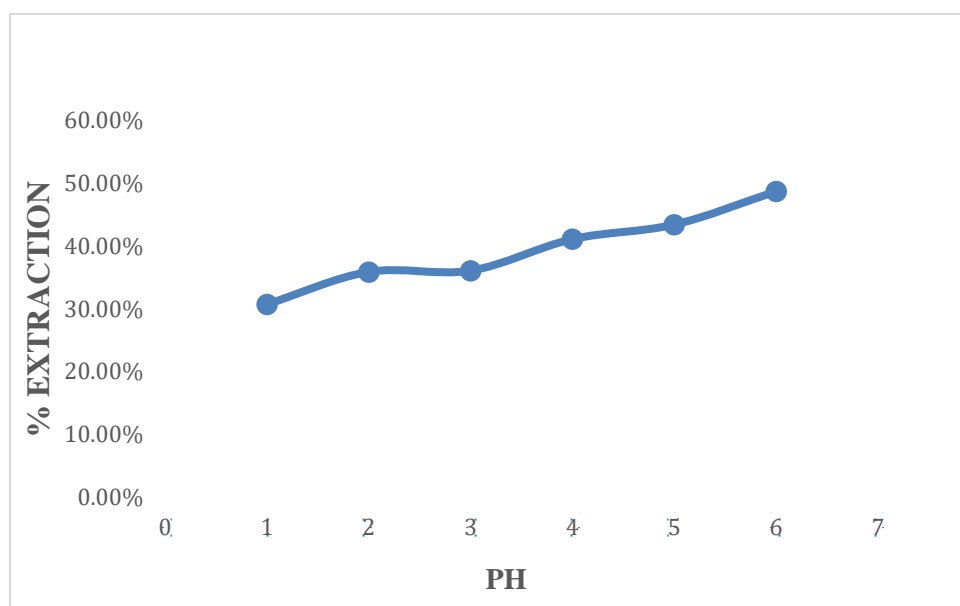


Fig. 2. Effect of pH % of Zn extracted

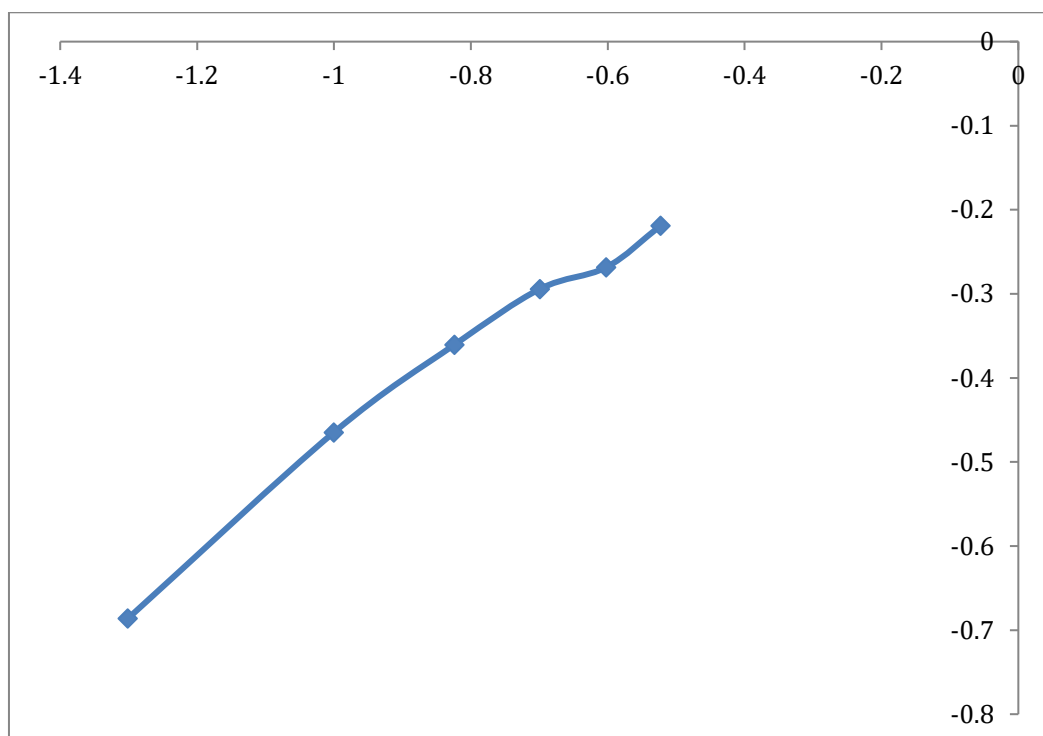


Fig. 3. Plot of log D against log [TBP]

4.5 Stripping Studies

The stripping study of Zn from the loaded TBP was carried out with a dilute HCl solution. The result of the stripping investigation showed that 0.05 mol/L HCl stripped Zn from the loaded TBP at a 1:1 phase ratio.

5. CONCLUSION

- ❖ The result obtained in the solvent extraction of Zn by TBP in kerosene, indicated that an increase in the initial extractant concentration (organic phase) enhanced the extracted percentage of Zn from burnt tyre ash with the highest percentage of Zn being 48.68% by 0.30 mol/L TBP at pH 4.5.
- ❖ The Liquid-Liquid Extraction of Zn^{2+} using Tributylphosphate in kerosene was found to have the potential of extracting Zn from burnt tyre ash leach liquor at the optimum condition with one mole of $[H^+]$ being liberated during extraction of one mole of Zn^{2+} from the burnt tyre ash.
- ❖ The study showed that a phase ratio of 1:1 for the organic phase; aqueous phase, extracted 48.68% of the total Zn into the organic phase at a pH of 4.5.

DISCLAIMER (ARTIFICIAL INTELLIGENCE)

Author(s) hereby declare that no generative AI technologies such as Large Language Models (ChatGPT, COPILOT, etc) and text-to-image generators have been used during the writing or editing of manuscripts.

ETHICAL APPROVAL

As per international standards or university standards written ethical approval has been collected and preserved by the author(s).

COMPETING INTERESTS

The authors have declared that no competing interests exist.

REFERENCES

1. Niezgodna A, Deng Y, Sabatier F, Ansart R. From end-of-life tires to storable energy carriers. Journal of Environmental Management. 2020;276:111318. Available: <https://doi.org/10.1016/j.jenvman.2020.111318>.
2. Malinova P. Effect of modified pyrolysis carbon on the properties of elastomer composites based on styrene-butadiene

- rubber. *Journal of Chemical Technology & Metallurgy*. 2022;57(4).
3. Xu J, Yu J, Xu J, Sun C, He W, Huang J, Li G. High-value utilization of waste tires: A review with focus on modified carbon black from pyrolysis. *Science of the total environment*. 2020;742: 140235. Available:<https://doi.org/10.1016/j.scitotenv.2020.140235>.
 4. Matinde E, Simate GS, Ndlovu S. Mining and metallurgical wastes: A review of recycling and re-use practices. *Journal of the Southern African Institute of Mining and Metallurgy*. 2018;118(8): 825-844.
 5. Šajin R, Ristović I, Čeplak B. Mining and Metallurgical Waste as Potential Secondary Sources of Metals—A Case Study for the West Balkan Region. *Minerals*. 2022;12(5):547.
 6. Akitoye, Adetoun, Nkwocha Stephen Tochi, Isaac Adebayo Akinbulu, Wesley Ohifeme Okiei, and Tiago Almeida Silva. Chitosan nanocomposites-based electrochemical sensors: A review. *International Research Journal of Pure and Applied Chemistry*. 2024;25(4):76-98. Available:<https://doi.org/10.9734/irjpac/2024/v25i4868>.
 7. Khatun J, Intekhab A, Dhak D. Effect of uncontrolled fertilization and heavy metal toxicity associated with arsenic (As), lead (Pb) and cadmium (Cd), and possible remediation. *Toxicology*. 2022;153274.
 8. Sathiyatiwat S. Recovery of zinc from metal-plating industrial wastewaters by liquid-liquid extraction. *Universidade do Algarve (Portugal)*; 2019.
 9. Krishnan S, Zulkapli NS, Kamyab H, Taib SM, Din MF BM, Abd Majid Z, Nasrullah M. Current technologies for recovery of metals from industrial wastes: An overview. *Environmental Technology & Innovation*. 2021;22:101525.
 10. Loy ACM, Yusup S, Lam MK, Chin BLF, Shahbaz M, Yamamoto A, Acda MN. The effect of industrial waste coal bottom ash as catalyst in catalytic pyrolysis of rice husk for syngas production. *Energy Conversion and Management*. 2018;165: 541-554.
 11. Kaya M, Hussaini S, Kursunoglu S. Critical review on secondary zinc resources and their recycling technologies. *Hydrometallurgy*. 2020;195:105362.
 12. Binnemans K, Jones PT, Manjón Fernández Á, Masaguer Torres V. Hydrometallurgical processes for the recovery of metals from steel industry by-products: A critical review. *Journal of Sustainable Metallurgy*. 2020;6:505-540.
 13. Kania H, Saternus M. Evaluation and current state of primary and secondary zinc production—A Review. *Applied Sciences*. 2023;13(3):2003.
 14. Tanong K, Tran LH, Mercier G, Blais JF. Recovery of Zn (II), Mn (II), Cd (II) and Ni (II) from the unsorted spent batteries using solvent extraction, electrodeposition and precipitation methods. *Journal of Cleaner Production*. 2017;148:233-244. Available:<https://doi.org/10.1016/j.jclepro.2017.01.158>.
 15. Jangid M, Rai AK, Sharma K, Vyas S, Ameta R, Ameta SC. Industrial applications of nonconventional solvents. *Organic Synthesis, Natural Products Isolation, Drug Design, Industry and the Environment*. 2023;249.
 16. Isak N, Xhaxhiu K. A review on the adsorption of diuron, carbaryl, and alachlor using natural and activated clays. *Remediation Journal*. 2023;201
 17. Jones F, Bankiewicz D, Hupa M. Occurrence and sources of zinc in fuels. *Fuel*. 2014;117:763-775. Available:<https://doi.org/10.1016/j.fuel.2013.10.005>
 18. Mielcarz-Skalska L, Smolińska B. Zinc and nano-ZnO—influence on living organisms. *Biotechnology and Food Science*. 2017; 81(2):93-102.
 19. Sabnavis M, Jagasheth UH, Avachat H, Mishra M. Zinc Industry: The unsung metal of the economy CARE ratings: Professional risk opinion, Report, 31st October; 2018.
 20. Sverdrup HU, Olafsdottir AH, Ragnarsdottir KV.). On the long-term sustainability of copper, zinc and lead supply, using a system dynamics model. *Resources, Conservation & Recycling: X*. 2019;4:100007. Available:<https://doi.org/10.1016/j.rcrx.2019.100007>.
 21. Yamada M, Ohira T, Watanabe N, Katagiri H, Shibayama A, Hamada F. Recovery of Pd (II) by solvent extraction with a dithiophenol-based extractant from the undiluted leachate of spent automotive catalysts followed by water scrubbing and thiourea stripping. *Hydrometallurgy*. 2023; 215:105986.

22. Mohammadzadeh M, Bagheri H, Ghader S. Solvent extraction of nickel and zinc from nitric acid solution using D2EHPA: experimental and modeling. Journal of Solution Chemistry. 2022;51(4):424-447.

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of the publisher and/or the editor(s). This publisher and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.

© Copyright (2024): Author(s). The licensee is the journal publisher. This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:

The peer review history for this paper can be accessed here:

<https://www.sdiarticle5.com/review-history/121724>